

Adsorption efficiency, thermodynamics and kinetics of Schiff base-modified nanoparticles for removal of heavy metals

M. K. Moftakhar¹ · M. R. Yaftian¹ · M. Ghorbanloo²

Received: 10 January 2015 / Revised: 18 February 2016 / Accepted: 20 February 2016 / Published online: 8 March 2016
© Islamic Azad University (IAU) 2016

Abstract Nanosilica particles modified by Schiff base ligands 3-methoxy salicylaldimine propyl triethoxysilane (MNS₁), 5-bromo salicylaldimine propyl triethoxysilane (MNS₂) and 3-hydroxy salicylaldimine propyl triethoxysilane (MNS₃) were prepared, and their potential for separation of copper, lead, zinc, cadmium, cobalt and nickel ions from aqueous solutions was examined. The effect of parameters influencing adsorption efficiency including aqueous-phase pH, amount of adsorbent, stirring time and initial concentration of the metal ions was assessed and discussed. Although MNS₁ and MNS₃ removed lead ions efficiently, all adsorbents showed strong selectivity toward copper ions. It was shown that, under some circumstances, MNS₃ decreased the amount of other ions, particularly cobalt, in the aqueous phase. The adsorbents were also applied for removal of copper and lead ions from real samples. Possible quantitative desorption of the metal ions loaded onto the adsorbents suggests their multiple uses in adsorption–desorption process. Investigation of temperature dependency of the process led to determination of the ΔH° , ΔS° and ΔG° values. This investigation indicates that the adsorption of copper ions onto the all studied adsorbents and lead ions onto MNS₁ and MNS₃ is endothermic. The Langmuir, Freundlich, Temkin and Dubinin–Radushkevich isotherms were tested to describe

the equilibrium data. Pseudo-first-order, pseudo-second-order, Elovich and intra-particle diffusion equations were applied to study the kinetics of copper and lead adsorption onto the modified nanoparticles. This investigation indicates that the process for all adsorbents follows pseudo-second-order kinetics and suggests a chemisorption mechanism for the adsorption processes by the studied adsorbents.

Keywords Heavy metals · Removal · Silica nanoparticles · Modification · Schiff base ligands

Introduction

Pollution created by heavy metals is a serious environmental issue (Agrawal 2009). The removal of these ions from wastewater is the subject of extensive fundamental and industrial research (Fu and Wang 2011). The recovery of some heavy metals from secondary sources may also have economic benefits (Hoque and Philip 2011).

Nanosized materials play a substantial role in metal ion separation owing to their physical and chemical properties. The potential of these materials for removal of biomolecules (Janschm et al. 2012), organic (Yu et al. 2014) and inorganic (Önnby et al. 2014) species has been widely investigated.

Schiff base ligands bearing nitrogen/oxygen donor atoms have been shown to exhibit ionophoric properties, especially toward heavy metal ions (Shokrolahi et al. 2007). These properties have been investigated by their application as modifier of octadecyl disks for separation-concentration of trace amounts of metal ions (Fathi et al. 2010; Shamsipur et al. 2000), as phase transfer agents of metal ions in liquid–liquid extraction (Oshima et al. 2003),

✉ M. R. Yaftian
yaftian@znu.ac.ir

¹ Phase Equilibria Research Laboratory, Department of Chemistry, Faculty of Science, University of Zanjan, P. O. Box 45371-38791, Zanjan, Iran

² Inorganic Chemistry Research Laboratory, Department of Chemistry, Faculty of Science, University of Zanjan, P. O. Box 45371-38791, Zanjan, Iran

as extractant in cloud point extraction procedures (Fathi and Yaftian 2009; Shemirani et al. 2006), as mobile carrier agents for the transport of metal ions through liquid membranes (Fathi et al. 2008) and as sensory molecules for preparation of cation-selective electrodes (Pilehvari et al. 2007).

Following our previous reports focused on the ionophoric properties of Schiff base receptors (Fathi et al. 2008; Fathi and Yaftian 2009; Fathi et al. 2010; Pilehvari et al. 2007) and the application of modified silica nanoparticles for removal of metal ions from water samples (Shiri-Yekta et al. 2013), the present study investigated the application of modified nanosilica particles (MNS) by three Schiff base ligands (Fig. 1) named 3-methoxy salicylaldehyde propyl triethoxysilane (MNS₁), 5-bromo salicylaldehyde propyl triethoxysilane (MNS₂) and 3-hydroxy salicylaldehyde propyl triethoxysilane (MNS₃) as adsorbents for removal of copper, lead, cobalt, nickel, zinc and cadmium ions from aqueous solutions. The parameters affecting the adsorption properties of the studied adsorbents were investigated and discussed. Experimental equilibrium data were evaluated using the Langmuir, Freundlich, Temkin and Dubinin–

Radushkevich isotherm models. Pseudo-first-order, pseudo-second-order, Elovich and intra-particle diffusion equations were tested to determine the kinetics of the adsorption process.

Beside the advantages of Schiff base ligands to bind efficiently heavy metal ions and the high surface area provided by nanosilica materials, the use of relatively low-cost materials in the preparation of the studied adsorbents allows this type of adsorbents to be considered as potential candidates for removal of heavy metal ions from water solutions. To the best of our knowledge, the preparation of the studied modified nanosilica particles and their application for removal of the target ions were not previously reported.

This study was wholly carried out at the Department of Chemistry, University of Zanjan (Iran), between November 2013 and October 2014.

Materials and methods

Chemicals

Methanol, toluene, amino propyl triethoxysilane, 2-hydroxy-3-methoxy benzaldehyde, 5-bromo-2-hydroxy benzaldehyde, 2,3-dihydroxy benzaldehyde, hydrochloric acid, nitric acid and sulfuric acid (Merck) were used as received. Unmodified nanoparticles (APS 20–30 nm) were purchased from Iranian Nanomaterial Pioneers. Stock solutions of the heavy metal ions (1000 mg L⁻¹) were prepared using corresponding nitrate salts (Merck or Fluka). The stock solutions were standardized complexometrically (Dean 1995). Working solutions were prepared by suitable dilution of the stock solutions with distilled water.

Apparatus

¹H NMR and ¹³C NMR measurements were taken using a FT-Bruker spectrometer (AVC 250 MHz), and the data were referenced relative to residual protonated solvents (7.26 ppm for CDCl₃). FT-IR spectra were recorded on a Thermo-Nicolet-is10 FT-IR spectrometer. The pH adjustments were performed using a Metrohm digital pH meter (model 780) equipped with a combined glass electrode. An Ika magnetic stirrer (MR 3001 K) was used for dispersing the adsorbent particles in the aqueous solutions. The temperature of the experiment vessels was controlled using a Julabo MP5 thermostat water circulator. Flame atomic absorption spectroscopy (FAAS; Varian 220AA) was used for metal ion determinations in water solutions. A furnace (Exiton, model Atash-1200) was used for activation of the silica nanoparticle surfaces before modification. The

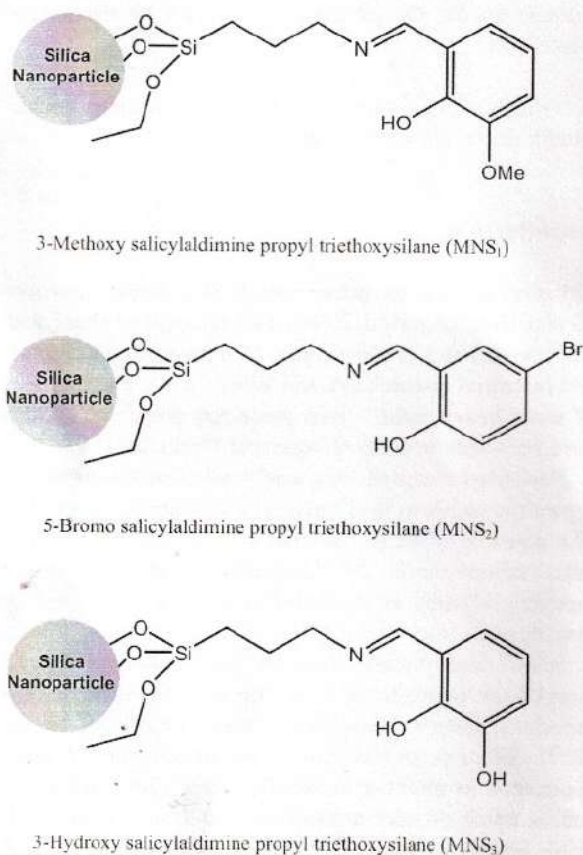


Fig. 1 Structure of the modified silica nanoparticles

separation of adsorbents from aqueous solution was assisted by a high-speed centrifuge (Sigma, 3–30 K). Distilled water was passed through a filter (TKA-Gen Pure) before use for preparation of aqueous solutions. The SEM photograph was taken by a Philips XL30 scanning microscope.

Preparation of adsorbents

Modification of silica nanoparticles was carried out according to the reported procedure elsewhere (Ghorbanloo et al. 2011). Condensation of amino propyl triethoxysilane with 2-hydroxy-3-methoxy benzaldehyde, 5-bromo-2-hydroxy benzaldehyde and 2,3-dihydroxy benzaldehyde in methanol produced 3-methoxy salicylaldehyde propyl triethoxysilane, 5-bromo salicylaldehyde propyl triethoxysilane and 3-hydroxy salicylaldehyde propyl triethoxysilane, respectively. The prepared Schiff base ligands were characterized by ^1H NMR, ^{13}C NMR and FT-IR spectra. By refluxing the synthesized Schiff base ligands with nanosized silica in toluene, the adsorbents MNS₁, MNS₂ and MNS₃ were resulted. Elemental analysis indicated that the amount of imine grafted on MNS₁, MNS₂ and MNS₃ was 0.34×10^{-3} , 0.44×10^{-3} and 0.49×10^{-3} mol imine g⁻¹, respectively. Figure 2 shows, as example, the SEM of the adsorbent MNS₁. SEM allowed examining the morphology and surface structure of the adsorbents at the required magnification.

Comparison of the FT-IR spectra of the unloaded and loaded modified adsorbents by copper ions was used for

characterization of the metal ion complexed by the ligating groups anchored on the adsorbents. A peak at 1653.5, 1648.3 and 1648.5 cm⁻¹ is attributed to the C=N bond for MNS₁, MNS₂ and MNS₃, respectively. After adsorption of copper ions, these peaks shift to the lower values at 1634.6, 1632.3 and 1647.4 cm⁻¹, respectively. This shift shows the participation of C=N bonds on the complexation of copper ions. The presence of water molecules prohibits characterizing the possible participation of oxygen atoms on the complexation of the metal ions.

Adsorption

The adsorption experiments were carried out in stoppered plastic vessels using 0.1 g of adsorbent in 20 mL of sample containing Cu²⁺, Pb²⁺, Co²⁺, Ni²⁺, Zn²⁺ and Cd²⁺ ions (20 mg L⁻¹). It was confirmed that adsorption equilibrium was reached after 50 min of magnetic stirring at 25 °C. After separation of the phases by centrifugation (20,000 rpm), the cation concentration remaining in the aqueous phase was measured by FAAS. The percentage of ion uptake and the percentage of ion desorption were calculated using Eqs. 1 and 2, respectively:

$$\text{Uptake \%} = \frac{(C_0 - C_e)}{C_0} \times 100 \quad (1)$$

$$\text{Desorption \%} = \frac{m_d}{m_a} \times 100 \quad (2)$$

where C_0 and C_e are the initial and equilibrium concentration of ions (mg L⁻¹), respectively, and m_d and m_a (mg) are the desorbed and adsorbed mass of ions, respectively.

Results and discussion

Effect of pH on adsorption

Since the ionization of hydroxyl groups of Schiff base ligands grafted onto the nanosilica matrix depends on the aqueous-phase pH, this parameter plays an important role on the adsorption efficiency. Figure 3 shows a significant increase in adsorption of copper ions by increasing the aqueous-phase pH. Similar result was observed for the adsorption of lead ions onto MNS₁ and MNS₃. An increase in the aqueous-phase pH reduces the competition of H⁺ ions and metal cations for adsorption sites. These finding suggest an ion exchange mechanism for the adsorption of the studied ions onto the adsorbents.

A comparison of the results obtained for unmodified nanoparticles (NS) and modified nanoparticles (MNS₁, MNS₂ and MNS₃) reveals that modification remarkably increases uptake of Cu²⁺ and Pb²⁺ ions. Although MNS₁

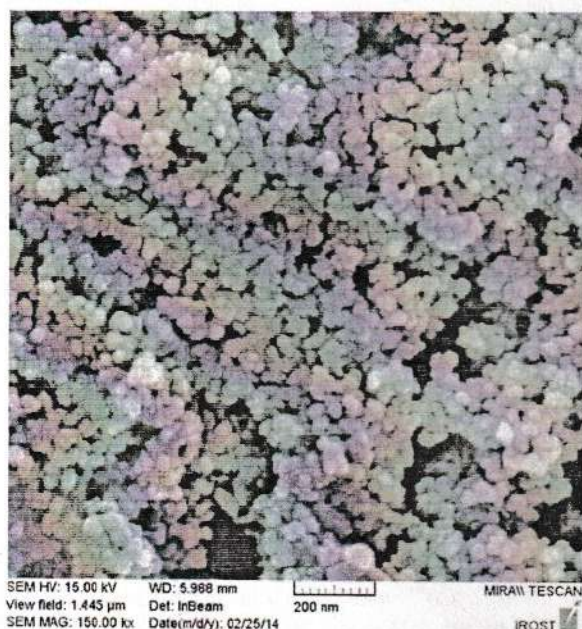


Fig. 2 SEM of the modified MNS₁



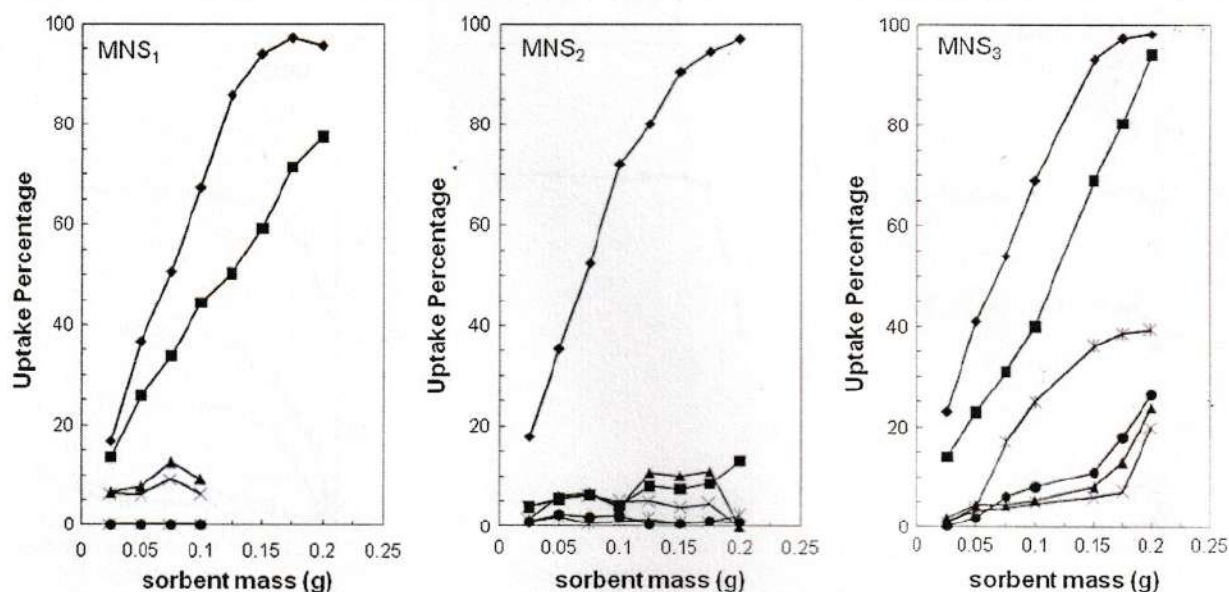


Fig. 4 Effect of amount of modified nanoparticles on adsorption efficiency of the studied metal ions (filled diamond Cu^{2+} , filled square Pb^{2+} , filled rectangle Zn^{2+} , times Cd^{2+} , asterisk Co^{2+} , filled circle

Ni^{2+}). Experimental conditions: initial concentration of metal ions 20 mg L^{-1} , aqueous-phase pH 5, stirring time 60 min, temperature 25°C

the metal ions, and thus an increase in metal ion uptake takes place (Zhang et al. 2012). It was found that the use of more than 0.15 g of MNS_1 , MNS_2 and MNS_3 results in quantitative removal of copper ions from the aqueous phase. Although an amount of more than 0.2 g of MNS_3 allows a quantitative elimination of lead ions, the lower efficiency of MNS_1 inhibits the removal of these ions more than 80 % by using the same mass of the adsorbent. The results obtained by MNS_3 show also the potential of this adsorbent toward other examined ions. It is found that, by using 0.2 g of MNS_3 , 40 % of cobalt ions and 20 % of zinc, cadmium and nickel ions can be removed from aqueous phase.

Time dependency of process

In order to optimize the time required for access to equilibrium condition, a series of adsorption experiments were performed. This investigation allows also verifying the kinetics of the process (see the section “kinetics of adsorption”). The adsorption of metal ions from aqueous solution (pH 5) using 0.1 g of adsorbent was studied by contacting the solid and liquid phases in the range 3–120 min (Fig. 5). Equilibrium of adsorption of copper ions was achieved after 10 min for MNS_1 , 20 min for MNS_2 and 50 min for MNS_3 . These results demonstrate that the kinetics of copper adsorption by MNS_1 is more rapid than by the other studied adsorbents. It is also seen that the adsorption of lead ions onto MNS_1 is more rapid than onto MNS_3 . An equilibrium condition for the removal

of cobalt ions by MNS_3 can be achieved after 60 min of stirring the phases.

Initial concentration of metal ions

It is found that an increase in initial metal ion concentration in the aqueous phase afforded an enhancement in the metal ion uptake (Fig. 6). The process was monitored by evaluating the maximum amount of metal ions adsorbed (q_m) by a given amount of adsorbent at pH 5. The q_m value for copper adsorption was 3.73 mg by MNS_1 , 4.12 mg by MNS_2 and 5.92 mg by MNS_3 , per g of adsorbent. This value was 1.69 and 5.82 mg lead per g of adsorbent for MNS_1 and MNS_3 , respectively. These values are in agreement with the order of the amount of imines grafted onto modified nanosilica particles, which was determined by elemental analysis, as 0.34×10^{-3} , 0.44×10^{-3} and $0.49 \times 10^{-3} \text{ mol imine g}^{-1}$ for MNS_1 , MNS_2 and MNS_3 , respectively.

Desorption

A series of adsorption experiments were performed to examine the possibility of multiple uses of the adsorbents and evaluate their stability. In these experiments, 20 mL of aqueous solution containing 20 mg L^{-1} of copper and lead ions adjusted to pH 5 was mixed with 0.2 g of the adsorbent and stirred magnetically for 60 min. After separation of the phases, the metal ions remained in the aqueous phase was analyzed. The results showed 100 % of Cu^{2+} ions by

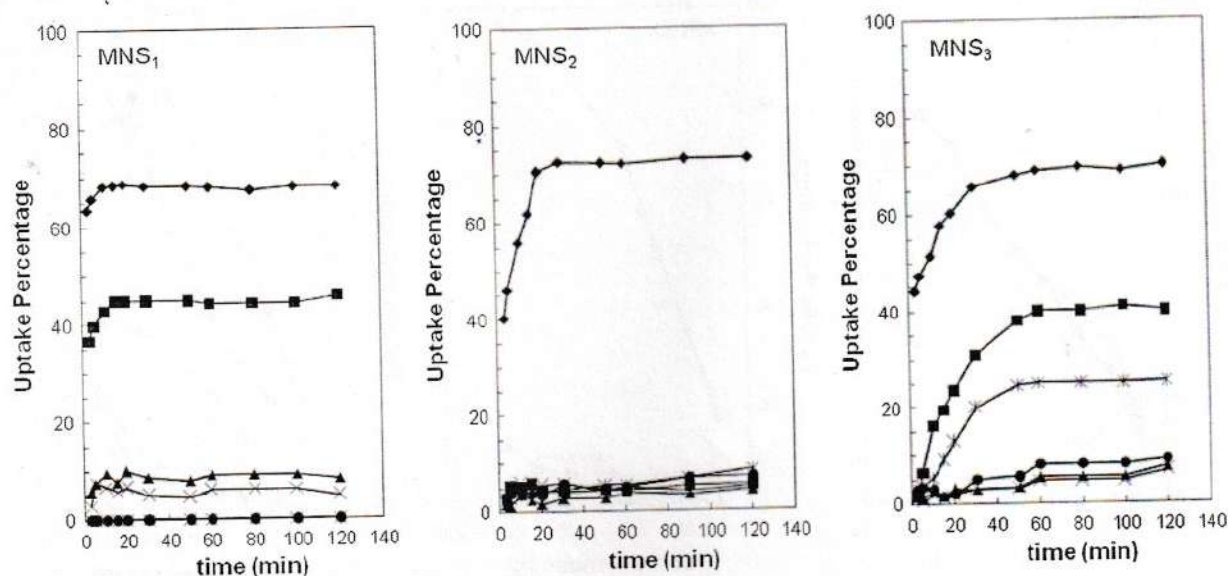


Fig. 5 Adsorption percentage of the studied metal ions (filled diamond Cu^{2+} , filled square Pb^{2+} , filled rectangle Zn^{2+} , times Cd^{2+} , asterisk Co^{2+} , filled circle Ni^{2+}) as a function of stirring time.

Experimental conditions: initial concentration of metal ions 20 mg L^{-1} , adsorbent 0.1 g , aqueous-phase pH 5, temperature 25°C

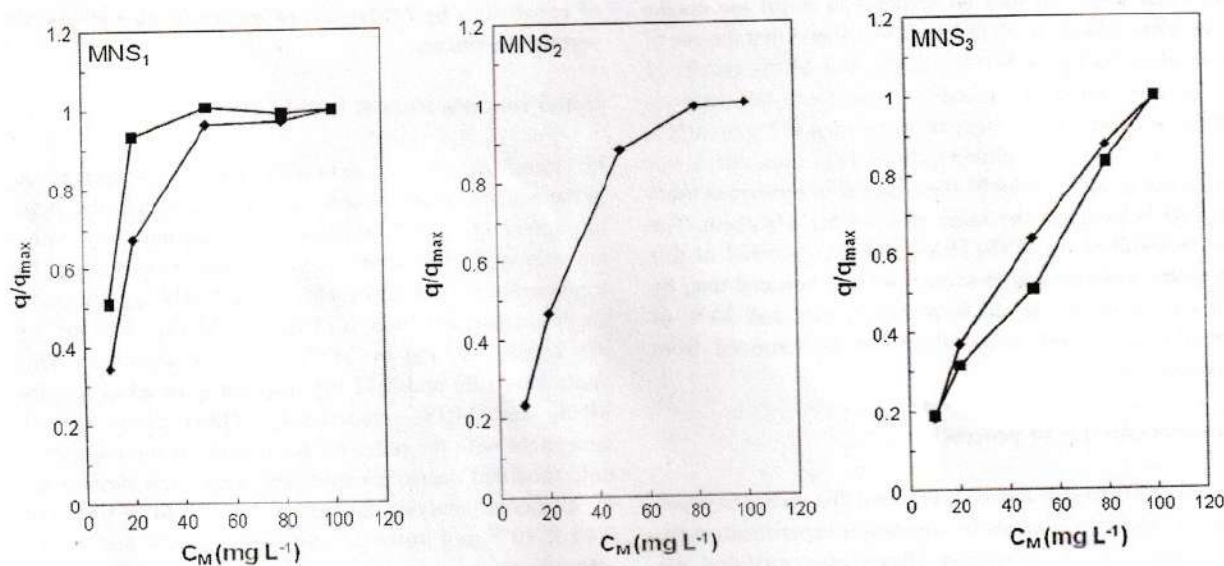


Fig. 6 Uptake of Cu^{2+} (filled diamond) and Pb^{2+} (filled square) ions by the studied adsorbents as a function of their initial concentrations in aqueous phase. Experimental conditions: adsorbent 0.15 g , aqueous-phase pH 5, stirring time 60 min , temperature 25°C

all the studied adsorbents and 80 % of lead ions by MNS_1 and 100 % of lead ions by MNS_2 were removed from the aqueous solutions. The adsorbents were washed twice using 5 mL of distilled water and then dried in an oven at 110°C . The loaded adsorbents were stripped with 5 mL of nitric acid, hydrochloric acid and sulfuric acid (0.1 mol L^{-1}) for 60 min (Table 1). It is seen that hydrochloric acid solution (5 mL , 0.1 mol L^{-1}) can quantitatively strip copper ions from MNS_1 and MNS_3 .

Quantitative stripping of lead ions from MNS_1 was achieved by hydrochloric or nitric acid solutions (0.1 mol L^{-1}). For a quantitative stripping of copper ions from loaded MNS_1 and lead ions from loaded MNS_2 , the stripped adsorbent from the first step was mixed with a second 5 mL solution of 0.1 mol L^{-1} hydrochloric acid. Under such conditions, all adsorbed metal ions transferred into the aqueous phase. The separated nanoparticles were used repeatedly for the experiments described above. There

Table 1 Comparison of various acid solutions as strippant of loaded adsorbents^a

Strippant (0.1 mol L ⁻¹)	MNS ₁		MNS ₂		MNS ₃	
	Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺
HCl ^b	100.0	100.0	81.5	—	98.7	78.0
HCl ^c	—	—	20.0	—	—	24.4
HNO ₃	87.8	100.0	84.7	—	87.0	61.5
H ₂ SO ₄	73.0	66.0	79.3	—	91.0	12.5

^a The values are in comparison with 100 % of the copper and lead ions loaded onto the adsorbents^b First stripping by 5 ml of hydrochloric acid^c Second stripping by 5 ml of hydrochloric acid**Table 2** Results of the experiments evaluating the applicability of the adsorbents for removal of copper and lead ions from real samples

Adsorbent	Well water		Tap water		Molten snow	
	Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺
MNS ₁	99.4 (±1.1)	99.2 (±1.4)	100.0 (±0.3)	93.5 (±0.6)	100.0 (±0.5)	96.5 (±0.2)
MNS ₂	98.8 (±0.3)	—	99.4 (±0.2)	—	99.6 (±0.1)	—
MNS ₃	99.8 (±0.2)	98.4 (±0.1)	100.0 (±0.5)	98.9 (±1.0)	100.0 (±0.6)	99.3 (±0.8)

Experimental conditions: aqueous phase, 20 mL of the samples injected by 20 mg L⁻¹ of copper and lead ions; pH 5; adsorbent dose 0.2 g; stirring time 60 min; temperature 25 °C

was no significant decrease (<5 %) in the determined adsorbent efficiency of the adsorbents after three adsorption–desorption cycles.

Applications

A series of experiments was designed to assess the applicability of the proposed method for removal of copper and lead ions from water samples. Three water samples (tap and well water samples from the University of Zanjan campus, and a sample of molten snow) were first digested by nitric acid solution. The resulting solutions were spiked with copper and lead ions (20 mg L⁻¹). A volume of 20 mL of samples adjusted to pH 5 was stirred with 0.2 g of adsorbent at room temperature. After 60 min of magnetic stirring, the solid particles were separated from the aqueous phase by centrifugation. The concentration of metal ions remaining in the aqueous phase was determined by FAAS. These experiments were repeated three times, and the results are shown in Table 2. It was found that copper ions were completely removed under selected conditions by all the examined adsorbents. A quantitative removal of Pb²⁺ ions was attained by using MNS₁ and MNS₂ adsorbents.

Temperature dependency and thermodynamics of process

To verify the influence of temperature on the process, the removal of Cu²⁺, Pb²⁺, Co²⁺, Ni²⁺, Zn²⁺ and Cd²⁺ ions

from their mixture by the modified nanoparticles was examined in the range 293–343 K. The distribution coefficient (K_d) was calculated as:

$$K_d = \frac{q_e}{C_e} \quad (3)$$

where q_e is the quantity of analyte adsorbed onto the adsorbent (mg g⁻¹) and C_e is the concentration of metal remaining in solution at equilibrium (mg L⁻¹).

The free energy changes (ΔG°) for the adsorption equilibrium is calculated from the distribution coefficients:

$$\Delta G^\circ = -RT \ln K_d \quad (4)$$

and is related to the enthalpy (ΔH°) and entropy (ΔS°) changes through the Gibbs–Helmholtz equation:

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (5)$$

It is possible to determine ΔG° , ΔH° and ΔS° using the plots of $\ln K_d$ versus T^{-1} and Eq. 6:

$$\ln K_d = -\frac{\Delta H^\circ}{RT} + \frac{\Delta S^\circ}{R} \quad (6)$$

Figure 7 reveals that adsorption efficiency increases as temperature increases. Table 3 lists the corresponding thermodynamic values. These values reveal that all adsorption processes were endothermic and controlled by changes in entropy. A positive change in enthalpy results from the dehydration of metal ions during adsorption (Tu et al. 2012). This dehydration requires an amount of energy that surpasses that from the heat released by the adsorption reaction (Liu et al. 2013).



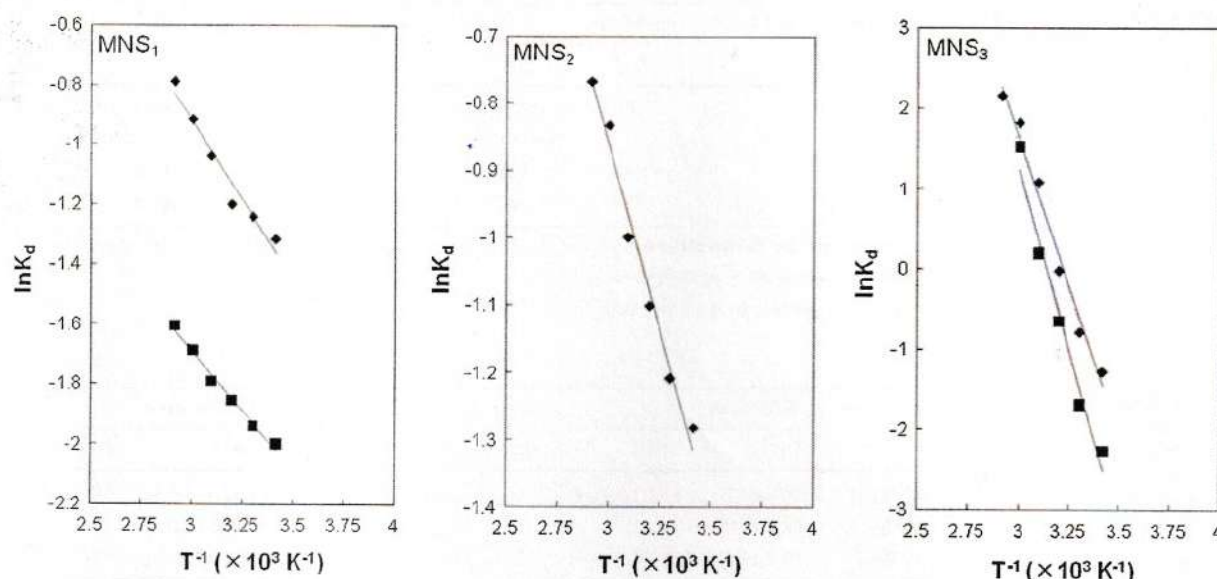


Fig. 7 Variation of $\ln K_d$ versus T^{-1} for adsorption of Cu^{2+} (filled diamond) and Pb^{2+} (filled square) ions onto MNS_1 , MNS_2 and MNS_3 . Experimental conditions: adsorbent 0.075 g, aqueous-phase pH 5; stirring time 60 min

Table 3 Thermodynamic parameters (in kJ mol^{-1}) for the adsorption of copper and lead ions onto MNS_1 , MNS_2 and MNS_3 at 298 K

Adsorbent	Metal ion	ΔH°	$T\Delta S^\circ$	ΔG°
MNS_1	Cu^{2+}	8.93	5.71	3.22
	Pb^{2+}	6.67	1.77	4.89
MNS_2	Cu^{2+}	9.04	5.95	3.10
	Pb^{2+}	—	—	—
MNS_3	Cu^{2+}	62.35	59.81	2.54
	Pb^{2+}	76.30	71.35	4.95

SD $< \pm 0.60$

Adsorption isotherms

To determine the most suitable isotherm for describing the experimental data, the Langmuir, Freundlich, Temkin and Dubinin–Radushkevich (D–R) isotherms were considered and applied to the experimental data.

The Langmuir isotherm considers monolayer coverage of the adsorption surface. The equation describing this isotherm is shown in Eq. 7:

$$\frac{C_e}{q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m} \quad (7)$$

in which C_e is the equilibrium concentration of metal ions in solution (mg L^{-1}), q_e is the amount of metal ions adsorbed per unit mass of adsorbent under equilibrium conditions (mg g^{-1}), q_m is the maximum adsorption capacity (mg g^{-1}), and K_L is the Langmuir constant

related to the adsorption energy (L mg^{-1}). A plot of C_e/q_e versus C_e allows determination of q_m and K_L . The separation factor or equilibrium parameter (R_L) is a useful dimensionless parameter which indicates the probability of the occurrence of adsorption. This parameter is expressed in Eq. 8:

$$R_L = \frac{1}{1 + K_L C_0} \quad (8)$$

A process is unfavorable if $R_L > 1.0$ or $R_L < 0$; is linear favorable if $R_L = 1$; and is favorable if the value of R_L falls between 0 and 1. An irreversible process occurs when $R_L = 0$ (Zhang et al. 2012).

The Freundlich isotherm suggests that the uptake of metal ions occurs on a heterogeneous surface by multilayer adsorption (Jiang et al. 2009). The mathematical expression for the Freundlich isotherm is shown by Eq. 9:

$$\log q_e = \log K_F + \frac{1}{n} \log C_e \quad (9)$$

where K_F and n are Freundlich constants for adsorption capacity and adsorption intensity, respectively. In this model, n is greater than unity and smaller value for $1/n$ indicates stronger interaction between adsorbent and solute.

The Temkin isotherm assumes that the heat of adsorption decreases linearly versus coverage rather than logarithmically, as for the Freundlich equation (Ghasemi et al. 2012). The equation describing this isotherm is:

$$q_e = \frac{RT}{b} \ln K_T + \frac{RT}{b} \ln C_e \quad (10)$$

where R is the gas constant ($0.0083 \text{ kJ mol}^{-1} \text{ K}^{-1}$), T is the absolute temperature (K), b is the Temkin constant related to heat of adsorption (kJ mol^{-1}), and K_T is the Temkin isotherm constant (L g^{-1}). Parameters K_T and b can be estimated by drawing the variation of q_e as a function of $\ln C_e$.

The D–R isotherm does not assume homogeneous or constant adsorption potential for the surface (Lin and Juang 2002). The equation describing D–R is given by Eq. 11:

$$\ln q_e = \ln q_m - K_{D-R} \varepsilon^2 \quad (11)$$

Here K_{D-R} ($\text{mol}^2 \text{ J}^{-2}$) is a constant related to adsorption energy and ε is the Polanyi potential as defined by Eq. 12:

$$\varepsilon = RT \ln \left(1 + \frac{1}{C_e} \right) \quad (12)$$

A plot of the variation of $\ln q_e$ as a function of ε^2 allows evaluating the parameters K_{D-R} and q_m . E is the mean energy (kJ mol^{-1}) required to bring a mole of adsorbate from infinity to the surface of the adsorbent (Ozcan et al. 2006). It can be calculated by Eq. 13:

$$E = \frac{1}{\sqrt{2K_{D-R}}} \quad (13)$$

This parameter is used to estimate the type of adsorption. The value of $E < 8 \text{ kJ mol}^{-1}$ shows a physical nature for the adsorption. Adsorption is explained by the ion exchange mechanism if E is greater than 8 and smaller than 16 kJ mol^{-1} .

The parameters for the Langmuir, Freundlich, Temkin and D–R isotherms are shown in Table 4. A comparison of R^2 values that correspond to the tested isotherms confirms that the adsorption of both copper and lead ions onto MNS_1 obeys the Langmuir model (Fig. 8a). The variation of $\ln q_e$ versus ε^2 based on the D–R isotherm presents two linear ranges. The R^2 of the second linear range indicates that this model is valid for the adsorption of copper onto MNS_1 in this region (Fig. 8b). Except for copper ion adsorption onto MNS_2 in the first linear range explained by D–R (Fig. 9d), the adsorption of ions onto MNS_2 could be described by all isotherms (Fig. 9).

Although the Langmuir isotherm was more suitable for lead ion adsorption onto MNS_3 (Fig. 10a), the removal of copper ions by this adsorbent obeyed both the Langmuir and Temkin isotherms (Fig. 10). The results for the Langmuir and D–R models (Table 4) show acceptable agreement between the calculated and experimental values of q_m ($q_{m,\text{exp}}$ and $q_{m,\text{cal}}$). The R_L values calculated by the Langmuir isotherm indicate that the processes were favorable. The n values derived from Freundlich isotherm reveal favorable processes for all types of adsorption. Table 4 shows that the values for $1/n$ derived from the

Freundlich model were 0.038–0.472. This confirms that the metal ions were favorably adsorbed by the modified adsorbents. Based on this parameter, the interaction between the adsorbed ion and the adsorbents varies as $\text{Pb}^{2+}/\text{MNS}_1 < \text{Cu}^{2+}/\text{MNS}_1 < \text{Cu}^{2+}/\text{MNS}_2 < \text{Pb}^{2+}/\text{MNS}_3 < \text{Cu}^{2+}/\text{MNS}_3$.

Table 5 shows the adsorption capacity and the time required for achieving equilibrium condition for the removal of copper and lead ions by the studied adsorbents in the present work, and those found by using the adsorbents *p*-dimethylaminobenzaldehyde-modified nanometer SiO_2 , SiO_2 -DMABD, (Cui et al. 2006), sodium dodecyl sulfate-coated poly(vinyl)chloride modified with bis(2-hydroxyacetophenone)-1,4-butanediimine, SDS-PVC-BHABDI, (Marahel et al. 2009) and Schiff base-modified nanocomposite, $\text{Fe}_3\text{O}_4/\text{SiO}_2$ -Pr-N = salicylaldehyde, (Moradinasab and Behzad 2014). The comparison of the data presented in Table 5 shows, although the capacity of SiO_2 -DMABD and modified nanocomposite $\text{Fe}_3\text{O}_4/\text{SiO}_2$ toward copper ions is remarkably higher than the studied adsorbents, these adsorbents are more efficacious materials with respect to the modified SDS-PVC adsorbent. MNS_3 shows comparable capacity toward lead ions in comparison with SiO_2 -DMABD. However, it presents higher adsorption potential toward lead ions than SDS-PVC-modified adsorbent. The time required for achieving equilibrium condition of adsorption of lead and copper ions (Table 5) reveals that the adsorption process onto MNS_1 is more rapid than the other compared adsorbents. It is seen that the equilibrium time for the copper adsorption by MNS_2 is reached after 20 min, which is the same as that for SiO_2 -DMABD. More rapid kinetics of the adsorption of copper ions was observed by MNS_1 , MNS_2 and MNS_3 , with respect to the modified nanocomposite $\text{Fe}_3\text{O}_4/\text{SiO}_2$.

Prediction of multi-component adsorption equilibrium


Multi-component adsorption systems involve competition among the heavy metals to occupy limited available adsorbent surface sites and the interactions between different adsorbates. Multi-component models are used to predict multi-component adsorptions equilibrium from single-component systems. Numerous models have been proposed to give a mathematical description of this proposition (Ho and McKay 2000; Wurster et al. 2000; Dabrowski et al. 2005). We selected Langmuir multi-component model, because the results of adsorption isotherms show this model describes suitably the single-component experimental results.

In order to correlate the results of multiple-component system to those of single component, Butler and Ockrent



Table 4 Parameters evaluated by using various isotherms for the adsorption of copper and lead ions onto the studied adsorbents


Isotherm type	Parameter	MNS ₁		MNS ₂		MNS ₃	
		Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺	Cu ²⁺	Pb ²⁺
Langmuir	$q_{m,exp}$ (mg g ⁻¹)	3.73	1.69	4.2	5.92	5.82	
	K_L (L mg ⁻¹)	0.78	3.31	0.57	0.14	0.27	
	$q_{m,cal}$ (mg g ⁻¹)	3.61	1.77	3.78	5.92	2.51	
	R_L	0.06	0.01	0.08	0.26	0.16	
	R^2	0.994	0.998	0.997	0.991	0.994	
Freundlich isotherm	K_F ((mg g ⁻¹)/(mg L ⁻¹) ^{1/n})	2.013	1.58	1.95	1.14	0.97	
	n	5.24	26.31	4.88	2.12	3.72	
	$1/n$	0.191	0.038	0.205	0.472	0.269	
	R^2	0.956	0.944	0.995	0.983	0.983	
		0.954	0.944	0.993	0.991	0.975	
Temkin isotherm	K_T (L g ⁻¹)	24.89	32.41	27.70	1.14	4.29	
	b (kJ mol ⁻¹)	4.28	37.43	4.34	1.72	5.04	
	R^2	0.954	0.944	0.993	0.991	0.975	
D-R isotherm	K_{D-R} (mol ² kJ ⁻²)	0.826	0.11	-0.95	2.91	1.93	
		0.052		0.15			
	$q_{m,cal}$ (mg g ⁻¹)	3.33	1.72	3.37	4.16	2.06	
		2.63		2.68			
	E (kJ mol ⁻¹)	0.78	2.15	—	0.42	0.51	
		3.10		1.81			
	R^2	0.887	0.946	0.931	0.908	0.894	
		0.999		0.998			

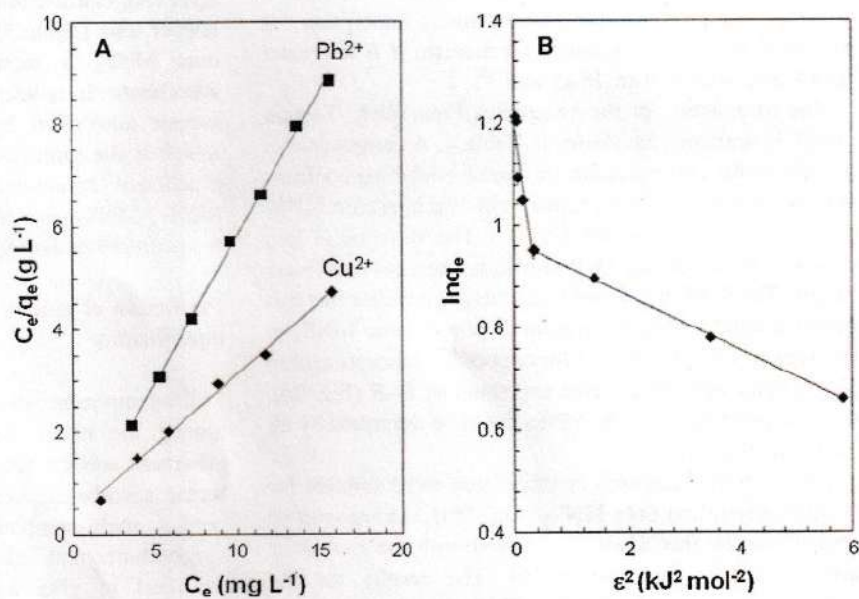Fig. 8 a Langmuir and b D-R isotherms for adsorption of Cu²⁺ (filled diamond) and Pb²⁺ (filled square) ions onto MNS₁

(1930) developed a model (BO model) based on the Langmuir equation. In these equations, it is assumed that each component adsorbs onto the surface according to ideal solute behavior under homogeneous conditions with no interaction or competition between molecules taking place.

It is widely used to calculate the Langmuir constant Q_m in multi-component systems. The common form for depicting the adsorbate distribution is to correlate the amount of solute adsorbed per unit weight of adsorbent with the residual solute concentration remaining in an equilibrium

Fig. 9 **a** Langmuir; **b** Freundlich; **c** Temkin; and **d** D-R isotherms for adsorption of Cu^{2+} ions onto MNS_2

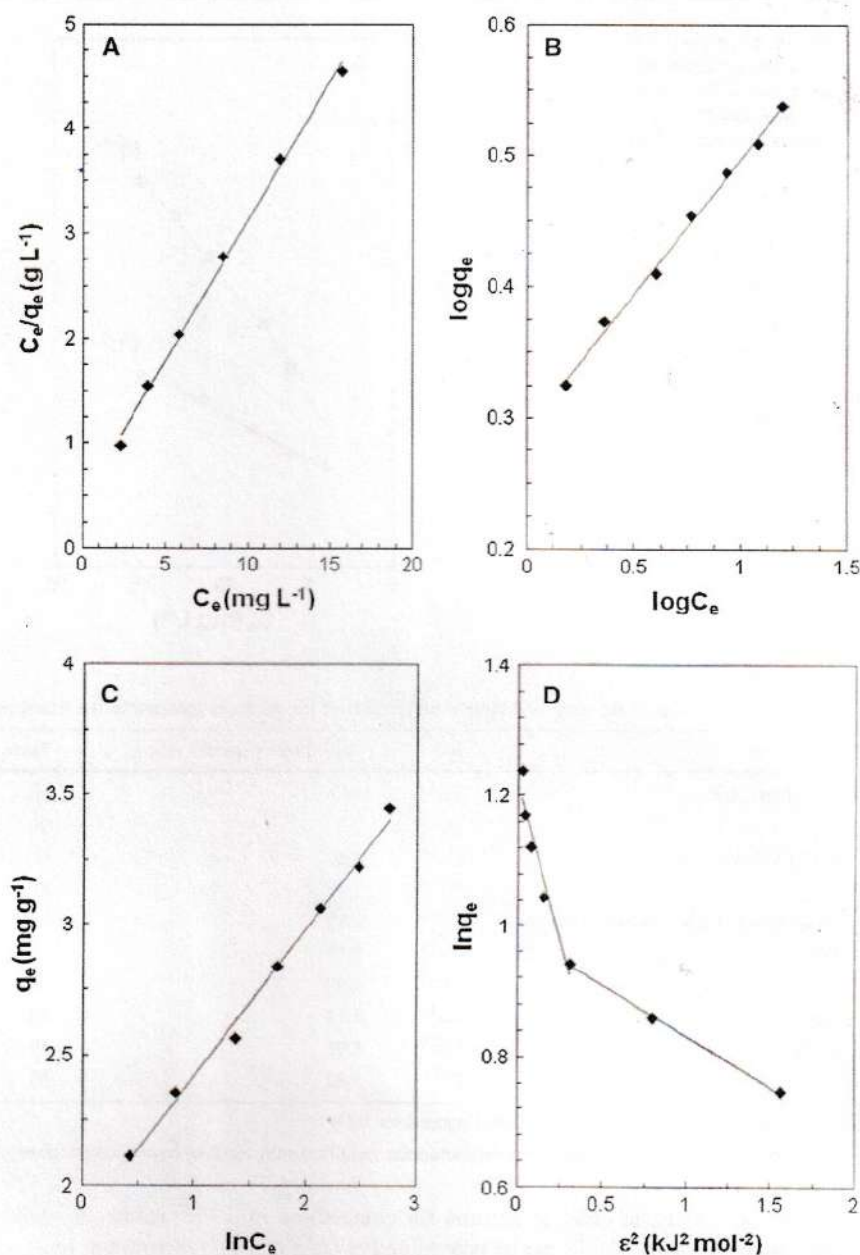

state. If there are two solutes present together in the adsorption system, the extended Langmuir isotherms are (Butler and Ockrent 1930):

$$Q_1 = \frac{q_{m,1} K_{L,1} C_{e,1}}{1 + K_{L,1} C_{e,1} + K_{L,2} C_{e,2}} \quad (14)$$

$$Q_2 = \frac{q_{m,2} K_{L,2} C_{e,2}}{1 + K_{L,1} C_{e,1} + K_{L,2} C_{e,2}} \quad (15)$$

where Q_1 and Q_2 are the amounts of solutes 1 and 2 adsorbed per unit weight of adsorbent at equilibrium concentrations $C_{e,1}$ and $C_{e,2}$, respectively. $q_{m,1}$ and $q_{m,2}$ are the

maximum adsorption capacities of solutes 1 and 2, respectively. These are determined from single-component systems and, therefore, correspond to monolayer coverage of the adsorbent. The parameters $K_{L,1}$ and $K_{L,2}$ are the Langmuir constants and are a function of the energy of adsorption of solutes 1 and 2, respectively, which are also determined from single-component systems.

The original competitive Langmuir model was improved by Jain and Snoeyink (1973). According to Jain and Snoeyink (JS) model, the Langmuir theory for binary adsorbate systems is based on adsorption without



Fig. 10 **a** Langmuir and **b** Temkin isotherms for adsorption of Cu^{2+} (filled diamond) and Pb^{2+} (filled square) ions onto MNS_3

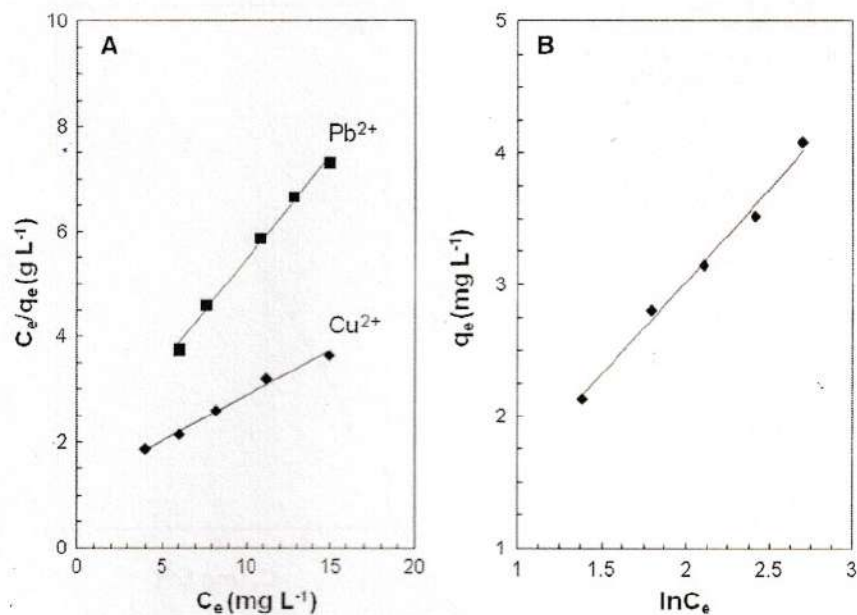


Table 5 Comparison of the proposed method with some of the methods reported in the literature

Adsorbent	Ion	Adsorption capacity (mg g^{-1})	Time (min)	References
$\text{SiO}_2\text{-DMABD}^a$	Cu^{2+}	18.6	20	Cui et al. (2006)
	Pb^{2+}	6	20	
SDS-PVC-BHABD^b	Cu^{2+}	2.6	60	Marahel et al. (2009)
	Pb^{2+}	2.2	60	
$\text{Fe}_3\text{O}_4@\text{SiO}_2\text{-Pr-N} = \text{salicylaldehyde}$	Cu^{2+}	97.2	60	Moradinasab and Behzad (2014)
	Cu^{2+}	3.73	10	
MNS_1	Pb^{2+}	1.69	10	Present work
	Cu^{2+}	4.12	20	
MNS_2	Cu^{2+}	5.92	50	Present work
MNS_3	Pb^{2+}	5.82	50	

^a p-Dimethylaminobenzaldehyde-modified nanometer SiO_2

^b Sodium dodecyl sulfate-coated poly(vinyl)chloride modified with bis(2-hydroxyacetophenone)-1,4-butanediimine

competition. Thus, in order to account for competition in the Langmuir theory, the JS model is proposed as (Jain and Snoeyink 1973):


$$Q_1 = \frac{(q_{m,1} - q_{m,2})K_{L,1}C_{e,1}}{1 + K_{L,1}C_{e,1}} + \frac{q_{m,2}K_{L,1}C_{e,1}}{1 + K_{L,1}C_{e,1} + K_{L,2}C_{e,2}} \quad (16)$$

The first term of Eq. 16 is the Langmuir expression for the number of molecules of solute 1 that are adsorbed without competition on the surface area and is proportional to $(q_{m,1} - q_{m,2})$. It is noteworthy that $q_{m,1} > q_{m,2}$. The second term in Eq. 16 represents the number of molecules of solute 1 adsorbed on the surface area proportional to $q_{m,2}$ in competition with solute 2. The number of molecules

of solute 2 adsorbed on the adsorbent surface is proportional to $q_{m,2}$ in competition with solute 1 and can be calculated from Eq. 15.

To predict the results of a multi-component adsorption system, the competitive Langmuir model (BO) and its modified model (JS) were both applied to Cu^{2+} and Pb^{2+} ions bisolute system. The obtained data for the adsorption studies are presented in Fig. 11. The low values of adsorbed copper ions predicted by BO model prohibited considering this model for extension of single-component experimental results to the competitive adsorption of copper in the presence of lead ions. This result is not surprising because the competitive Langmuir model is thermodynamically consistent only in the special case where the capacities of the adsorbates are equal. Therefore, it seems

Fig. 11 Prediction of the competitive removal of Cu^{2+} and Pb^{2+} ions based on the BO and JS models onto MNS_1 and MNS_3 . Filled diamond Single-component system, filled square BO prediction, filled rectangle JS prediction

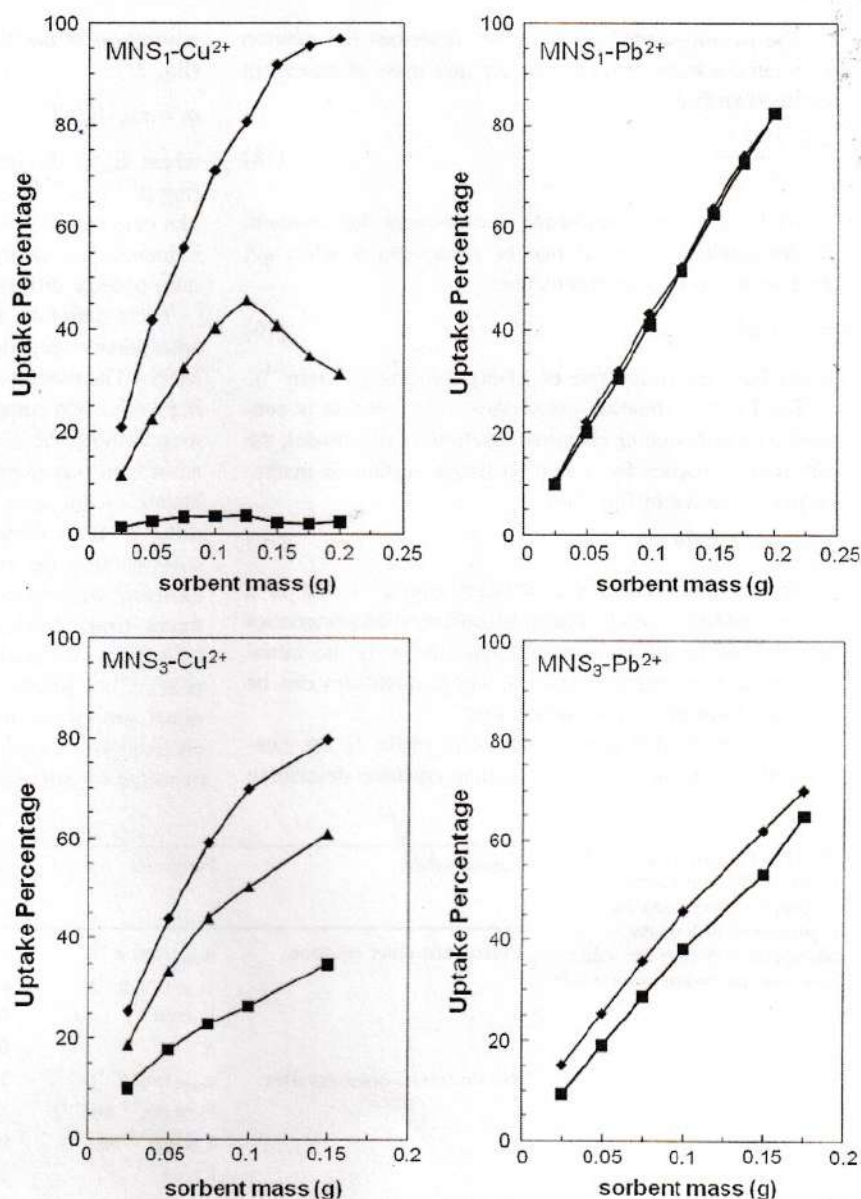

that the predicted values estimated by JS model are more close to that can be obtained experimentally.

However, JS model predicts that although the competition of copper and lead ions adsorption on MNS_3 was not altered by adsorbent dose, it is seen that an inverse selectivity in favor of lead ions can be predicted beyond 0.125 g of the adsorbent MNS_1 .

Kinetics of adsorption

Pseudo-first-order, pseudo-second-order, simple Elovich and intra-particle diffusion kinetic models are conventional

models examined to investigate the kinetics of adsorption processes (Nameni et al. 2008; Mohaptra et al. 2009). The pseudo-first-order kinetics model assumes that adsorption is controlled by the diffusion step and its adsorption is proportional to the difference in adsorption capacity at equilibrium and at any time t (q_e and q_t , respectively, in mg g^{-1}). This model is mathematically described by Eq. 17:

$$\log(q_e - q_t) = \log q_e - \frac{k_{1,\text{ads}}}{2.303} t \quad (17)$$

where $k_{1,\text{ads}}$ is the pseudo-first-order rate constant.

Conclusion

Nanosilica particles modified with Schiff base ligands 3-methoxy salicylaldimine propyl triethoxysilane (MNS₁), 5-bromo salicylaldimine propyl triethoxysilane (MNS₂) and 3-hydroxy salicylaldimine propyl triethoxysilane (MNS₃) are potential adsorbents for selective removal of copper and lead ions from aqueous solutions. MNS₂ demonstrated excellent selectivity for removal of copper ions. Although the efficiency of MNS₃ for removal of Zn²⁺, Cd²⁺, Co²⁺ and Ni²⁺ ions was shown, more investigation is required to optimize the experimental conditions for quantitative removal of these ions from aqueous solutions.

Adsorption-desorption of the metal ions onto the adsorbents allow their use repeatedly for removal of copper and lead ions from aqueous solutions. Evaluated thermodynamic parameters indicated that the adsorption processes were endothermic and controlled by entropy changes. The isotherms describing the experimental results of adsorption depend on the metal ions and type of adsorbent. The adsorption kinetics were described by considering pseudo-second-order reaction with chemisorption as the rate-limiting mechanism. The Elovich equation indicates both the chemisorption nature of adsorption and the heterogeneous surface of adsorbent.

Acknowledgments The authors would like to thank the University of Zanjan for their financial support (Grant Number EA/7774 21-11-2013) of this study.

References

- Agrawal SK (2009) Heavy metal pollution. A. P. H. Publishing Corporation, New Delhi
- Bhattacharya AK, Naiya TK, Mondal SN, Das SK (2008) Adsorption, kinetics and equilibrium studies on removal of Cr(VI) from aqueous solutions using different low-cost sorbents. *Chem Eng J* 137:529–541
- Butler JAV, Ockrent C (1930) Studies in electrocapillarity. Part III. The surface tensions of solutions containing two surface-active solutes. *J Phys Chem* 34:2841–2859
- Cui Y, Chang X, Zhai Y, Zhu X, Zheng H, Lian N (2006) ICP-AES determination of trace elements after preconcentrated with p-dimethylaminobenzaldehyde-modified nanometer SiO₂ from sample solution. *Microchem J* 83:35–41
- Dabrowski A, Podkościelny P, Hubicki Z, Barczak M (2005) Adsorption of phenolic compounds by activated carbon: a critical review. *Chemosphere* 58:1049–1070
- Dean JA (1995) Analytical chemistry handbook. McGraw-Hill, New York
- Fathi SAM, Yafian MR (2009) Cloud point extraction and flame atomic absorption spectrometry determination of trace amounts of copper(II) ions in water samples. *J Colloid Interface Sci* 334:167–170
- Fathi SAM, Parinejad M, Yafian MR (2008) Multidentate nitrogen/oxygen donor ionophores; their use as selective extracting and mobile-carrier agents for copper(II) ions. *Sep Purif Technol* 64:1–7
- Fathi SAM, Rostamkhani S, Yafian MR (2010) Determination of trace amounts of copper in water samples by flame atomic absorption spectrometry after preconcentration on octadecyl-bonded silica membranes modified by a di-Schiff base ligand. *J Anal Chem* 65:614–619
- Fu F, Wang Q (2011) Removal of heavy metal ions from wastewaters: a review. *J Environ Manag* 92:407–418
- Ghasemi Z, Seif A, Ahmadi TS, Zargar B, Rashidi F, Rouzbahani GM (2012) Thermodynamic and kinetic studies for the adsorption of Hg(II) by nano-TiO₂ from aqueous solution. *Adv Powder Technol* 23:148–156
- Ghorbanloo M, Monfared HH, Janiak C (2011) The catalytic function of a silica gel-immobilized Mn(II)-hydrazide complex for alkene epoxidation with H₂O₂. *J Mol Catal A: Chem* 345:12–20
- Ho YS (2006) Isotherm for the sorption of lead onto peat: comparison of linear and non-linear methods. *Pol J Environ Stud* 15:81–86
- Ho YS, McKay G (2000) Correlative biosorption equilibria model for a binary batch system. *Chem Eng Sci* 55:817–825
- Hoque ME, Philip OJ (2011) Biotechnological recovery of heavy metals from secondary sources: an overview. *Mater Sci Eng* 31:57–66
- Jain JS, Snoeyink VL (1973) Adsorption from bisolute systems on active carbon. *J Water Pollut Control Fed* 45:2463–2479
- Jansch M, Stumpf P, Graf C, Rühi E, Müller RH (2012) Adsorption kinetics of plasma proteins on ultrasmall superparamagnetic iron oxide (USPIO) nanoparticles. *Int J Pharm* 428:125–133
- Jiang Y, Pang H, Liao B (2009) Removal of copper(II) ions from aqueous solution by modified bagasse. *J Hazard Mater* 164:1–9
- Lin S, Juang R (2002) Heavy metal removal from water by sorption using surfactant modified montmorillonite. *J Hazard Mater* 92:315–326
- Liu Y, Chen M, Hao Y (2013) Study on the adsorption of Cu(II) by EDTA functionalized Fe₃O₄ magnetic nano-particles. *Chem Eng J* 218:46–54
- Marahel F, Ghaedi M, Shokrollahi A, Montazerzohori M, Davoodi S (2009) Sodium dodecyl sulfate coated poly(vinyl) chloride: an alternative support for solid phase extraction of some transition and heavy metals. *Chemosphere* 74:583–589
- Mohapatra M, Khatun S, Andad S (2009) Adsorption behavior of Pb(II), Cd(II) and Zn(II) on NALCO plant sand. *Indian J Chem Technol* 16:291–300
- Moradinassab S, Behzad M (2014) Removal of heavy metals from aqueous solution using Fe₃O₄ nanoparticles coated with Schiff base ligand. *Desalin Water Treat* 52:1–9
- Nameni M, Alavi Moghadam MR, Arami M (2008) Adsorption of hexavalent chromium from aqueous solutions by wheat bran. *Int J Environ Sci Technol* 5:161–168
- Önby L, Svensson C, Mbundi L, Busquets R, Cundy A, Kirsebom H (2014) γ-Al₂O₃-based nanocomposite adsorbents for arsenic(V) removal: assessing performance, toxicity and particle leakage. *Sci Total Environ* 473–474:207–214
- Oshima S, Hirayama N, Kubono K, Kokusen H, Honjo T (2003) Ion-pair extraction behavior of divalent metal cations using neutral di-Schiff base ligands derived from 1,2-cyclohexanediamine and o-phenylenediamine. *Talanta* 59:867–874
- Ozcan A, Oncu EM, Ozcan AS (2006) Kinetics, isotherm and thermodynamic studies of adsorption of acid blue 193 from aqueous solutions onto natural sepiolite. *Colloid Surf A* 277:90–97
- Pilehvari Z, Yafian MR, Rayati S, Parinejad M (2007) A novel wire-type lead-selective electrode based on bis(1'-hydroxy-2'-acet-naphthone)-2,2'-diiminodiethylamine. *Ann Chim* 97:747–757
- Shamsipur M, Ghiasvand AR, Sharghi H, Naeimi H (2000) Solid phase extraction of ultra trace copper(II) using octadecyl silica



- membrane disks modified by a naphthol-derivative Schiff's base. *Anal Chim Acta* 408:271–277
- Shemirani F, Jamali MR, Kozani RR, Salavati-Niasari M (2006) Cloud point extraction and preconcentration for the determination of Cu and Ni in natural water by flame atomic absorption spectrometry. *Sep Sci Technol* 41:3065–3077
- Shiri-Yekta Z, Yaftian MR, Nilchi A (2013) Silica nanoparticles modified with a Schiff base ligand: an efficient adsorbent for Th(IV), U(VI) and Eu(III) ions. *Korean J Chem Eng* 30:1644–1651
- Shokrolahi A, Ghaedi M, Ghaedi H (2007) Potentiometric and spectrophotometric studies of copper(II) complexes of some ligands in aqueous and nonaqueous solution. *J Chin Chem Soc* 54:933–940
- Tu YJ, You CF, Chang CK (2012) Kinetics and thermodynamics of adsorption for Cd on green manufactured nano-particles. *J Hazard Mater* 235–236:116–122
- Wurster DE, Alkhamis KA, Matheson LE (2000) Prediction of Adsorption from multicomponent solutions by activated carbon using single-solute parameters. *AAPS Pharm Sci Tech* 1(3): article 25
- Yu JX, Chi RA, Zhang YF, Xu ZG, Xiao CQ, Guo J (2012) A situ co-precipitation method to prepare magnetic PMDA modified sugarcane bagasse and its application for competitive adsorption of methylene blue and basic magenta. *Bioresour Technol* 110:160–166
- Yu J-G, Zhao X-H, Yang H, Chen X-H, Yang Q, Yu L-Y, Jiang J-H, Chen X-Q (2014) Aqueous adsorption and removal of organic contaminants by carbon nanotubes. *Sci Total Environ* 482–483:241–251
- Zhang X, Jiao C, Wang J, Liu Q, Li R, Yang P, Zhang M (2012) Removal of uranium(VI) from aqueous solutions by magnetic Schiff base: kinetic and thermodynamic investigation. *Chem Eng J* 198–199:412–419
- Zhou YT, Christopher BW, Nie HL (2009) Adsorption mechanism of Cu^{2+} from aqueous solution by chitosan-coated magnetic nanoparticles modified with α -ketoglutaric acid. *Colloid Surf B* 74:244–252
- Zhou LM, Jin JY, Liu ZR, Liang XZ, Shang C (2011) Adsorption of acid dyes from aqueous solutions by the ethylenediamine-modified magnetic chitosan nanoparticles. *J Hazard Mater* 185:1045–1052